

Energetics of the oxidation and opening of a carbon nanotube

M. S. C. Mazzoni,^{*} H. Chacham,^{*} P. Ordejón,[†] D. Sánchez-Portal,[‡] J. M. Soler,[‡] and E. Artacho[‡]

^{*}*Departamento de Física, ICEx, Universidade Federal de Minas Gerais. C.P. 702, 30123-970 Belo Horizonte, MG, Brazil*

[†]*Departamento de Física, Universidad de Oviedo, 33007 Oviedo, Spain*

[‡]*Departamento de Física de la Materia Condensada, C-III, Universidad Autónoma de Madrid, 28049 Madrid, Spain*

(27 May 1999)

We apply first principles calculations to study the opening of single-wall carbon nanotubes (SWNT's) by oxidation. We show that an oxygen rim can stabilize the edge of the open tube. The sublimation of CO₂ molecules from the rim with the subsequent closing of the tube changes from endothermic to exothermic as the tube radius increases, within the range of experimental feasible radii. We also obtain the energies for opening the tube at the cap and at the wall, the latter being significantly less favorable.

PACS Numbers: 61.48.+c, 71.20.Tx, 71.15.Nc

The possibility of filling carbon nanotubes [1] with a variety of substances has fascinated the materials science community since they were first observed [2] and synthesized in promising quantities [3], but the fact that the tube tips are closed represented a severe limitation for it. Ajayan and Iijima [4] observed the cap removal and filling of the nanotubes when they were heated in air, suggesting a chemical reaction between oxygen and the tube ends. This was confirmed by Ajayan et al [5] who showed that the tubes were open exclusively at the caps. Simultaneously, Tsang, Harris and Green [6] described the thinning and opening of nanotubes by carbon dioxide. They also observed corrosion at the cap region, the tube walls remaining intact. Ugarte et al [7] described a method of filling nanotubes in which they were first oxidized in air to remove the caps. In this process, 60% of the tubes were open. The above mentioned experiments used multi-walled nanotubes. In a recent experiment, however, Dillon *et al.* [8] observed the physisorption of H₂ in bundles of small-diameter SWNT's. They suggested that these tubes were open by oxidation in the same way as multi-walled tubes. Individual open-ended SWNT's were also obtained experimentally [9] by treating SWNT rope material with a mixture of acids.

The filling and opening of nanotubes have also been subjects of theoretical studies. Pederson and Broughton [10] predicted the tendency of the nanotubes to attract molecules to their interior. More recently, Miyamoto et al [11] reported first-principles calculations that showed the ionic cohesion between carbon nanotubes and potassium atoms linearly arranged inside them. The reactivity of the open end of SWNT's was studied by Charlier et al [12]. They showed that the unsaturated tip of small diameter SWNT's closes spontaneously at typical growth temperatures. However, first principles calculations also indicate that these tubes may stay open during growth in the presence of a catalyst, such as Ni [13].

The detailed description of the burning and opening processes, and of their kinetics, is a formidable problem beyond the scope of state-of-art ab initio techniques. In

the present work, we apply first principles calculations to address two specific, but relevant questions on the energetics of these processes: (i) why does O₂ attack preferentially the tube caps? and (ii) how and why do the tubes remain open (if at all) after the O₂ supply has been cut? To address the first question, we compare the opening of oxidized holes at the cap of the tube with their chemical equivalents at the wall, finding that the cap oxidation is much more favorable, due to the release of its curvature strain. On the second question, we find that the presence of an oxygen rim at the edge of the open tube results in a very stable configuration, even in the absence of O₂. Smaller holes with favorable energetics allow us to obtain an estimate of the activation barrier of the closing process.

Our calculations were performed with the SIESTA program [14–16], using density-functional theory [17], within the generalized gradient approximation (GGA) for exchange-correlation [18], and norm-conserving pseudopotentials [19,20]. The basis set is a linear combination of pseudoatomic orbitals [21,22]. We always used a split-valence double- ζ (DZ) basis [23], and convergence tests were performed by adding polarization functions [24]. This resulted in changes in formation energies of only a few meV/atom. All the geometries were optimized, with remanent forces of less than 0.1 eV/Å. Test calculations were performed on graphite, nanotubes, and fullerenes. The calculated nearest-neighbor distances of C₆₀ (1.42 and 1.47 Å) and graphite (1.42 Å) reproduce the experimental values (1.40, 1.46, and 1.42 Å, respectively) [1] within 2%. Also, the energy per atom of C₆₀ relative to that of graphite (0.38 eV/atom) agrees very well with the experimental result (0.392 - 0.433 eV/atom) [25]. Our calculations were performed for (4,4), (6,6), and (8,8) armchair SWNT's, with diameters 5.6, 8.3, and 11.1 Å, containing up to 166 carbon atoms. However, for the sake of clarity in the exposition, we will refer to the specific (6,6) case throughout the paper, leaving the analysis of the size effects to the end.

In order to understand why O₂ produces a selective ox-

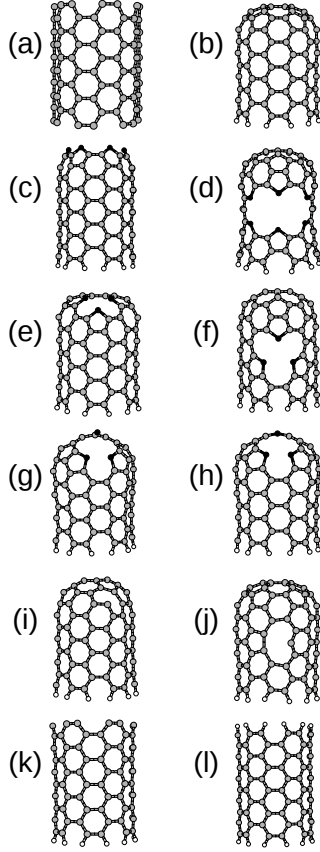


FIG. 1. Structures used in the calculations for the (6,6) carbon nanotube. (a) Infinite tube (periodic boundary conditions); (b) closed tube, with 120 carbon atoms and 12 hydrogen atoms saturating the bulk-like end of the tube; (c) oxidized open tube; (d) oxidized opening equivalent to (c) but at the wall instead of the cap; (e) oxidized hole obtained by removing a hexagon at the cap; (f) same as (e) at the wall; (g) oxidized hole obtained by removing a pentagon; (h) same as (g) but removing an additional C atom; (i) a C vacancy at the cap; (j) vacancy at the wall; (k) unsaturated open tube; (l) H-saturated open tube on both sides (used to characterize the saturation energy). The free H_2 , O_2 , H_2O , and CO_2 molecules were also calculated. The back atoms are not shown in the figure.

idation of the tube caps, rather than a generalized burning, we compare the energies of similar holes at the tube’s cap and wall. Figure 1 shows these structures for the (6,6) tube. The closed tube, hereafter denoted by C_{120} , is shown in Fig. 1(b). The other end of the tubes is bulk-like and saturated by hydrogen atoms. This termination is used in all the structures, except the infinite tubes used to calculate the carbon chemical potential μ_C , for which we used periodic boundary conditions [Fig. 1(a)]. The hole geometries, shown in Fig. 1(c)-(j), were chosen as plausible low energy structures for specific hole sizes and not necessarily to simulate the actual oxidation process.

These hole structures will provide estimates of the energy released, for a given hole size, during the tube opening process. Figure 2 shows the potential energy change during oxidation as a function of the hole size, measured by the number of carbon atoms lost by the tube in the process. These atoms are removed from the tube according to the reaction $\text{C} + \text{O}_2 \rightarrow \text{CO}_2$, while extra oxygen is used to saturate the resulting holes. The initial structure is Fig. 1(b) and the oxidized structures are Fig. 1(c)-(j). The general trend is linear with the number of C atoms missing in the hole, as it should, but the energy released by oxidizing the cap is larger than for the wall, as shown in Fig. 2(b) [26]. As we will see, the origin of the difference is the extra elastic energy accumulated at the cap. It is remarkable that the wall-cap difference for removing the first carbon atom (2.4 eV), is already very close to that for a full hexagonal hole. Thus, the cap’s strain energy is substantially released from the very beginning of the oxidation.

Addressing the stability of the open tube after oxidation, Fig 1(c) shows the most efficient chemical saturation of the open tube with oxygen. In this oxidized open tube, denoted by C_{120}O_6 , every O atom saturates two carbon “dangling bonds”, giving a slightly stretched C-O bond distance of 1.43 Å and a C-O-C angle of 105° . The bond stretching produces an inward relaxation (18°) of the rim structure as a consequence of the pulling of the O atoms, diminishing the tube perimeter at the rim. The structure is very stable: the sublimation of oxygen atoms in the form of CO_2 , resulting in an unsaturated open tube [Fig. 1(k)], is found to be energetically unfavorable by 17.8 eV. This highly endothermic reaction indicates that, if open tubes are present, they will have an oxygen rim at the edge even at typical oxidation temperatures ($\sim 1000\text{K}$) [27].

Starting with this oxidized open tube, we consider a reaction in which the tube closes and CO_2 molecules evaporate:



The energy of this reaction is $\Delta E = (E_{\text{C}_{120}} + 3E_{\text{CO}_2}) - (E_{\text{C}_{120}\text{O}_6} + 3\mu_C)$. The result is $\Delta E = 0.2$ eV with the DZ basis, and $\Delta E = 0.3$ eV including polarization orbitals. Thus, the oxidized open tube is slightly favorable energetically over the closed one for this tube diameter. However, it has to be stressed that the system composed by the closed tube and the carbon dioxide gas has larger entropy and will thus predominate in thermodynamic equilibrium at a high enough temperature.

In addition to its genuine stability, the oxidized open tube can be further stabilized by the energy barrier of the closing process, which requires substantial rebonding. The actual rebonding is extremely hard to guess or simulate. We search for an estimate of the energy barrier as follows: first we consider a “closing coordinate” that the system must necessarily follow during the

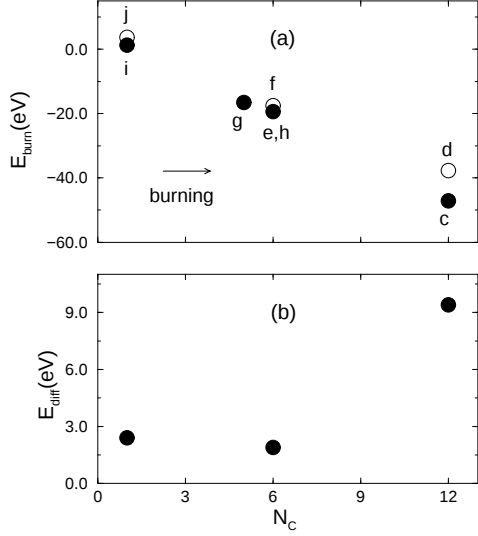


FIG. 2. (a) Potential energy change, E_{burn} , during the burning process of the original closed tube, leaving behind the holes shown in Fig. 1. E_{burn} is plotted versus the number of C atoms missing in the final hole. Filled symbols are for holes at the cap of the tube, open symbols for holes at the wall. The labels refer to the structures of Fig. 1. (b) Energy difference between burning the tube at the wall or at the cap: $E_{diff} = E_{burn}^{wall} - E_{burn}^{cap}$.

closing process. We simply use the hole size, defined as before as the number of carbon atoms missing from the closed tube. Then, for particular values of this coordinate, we search for low energy structures using basic chemical principles: to break the minimum number of the most strained C-C bonds, and to saturate them with oxygen. The chosen structures are those in Fig. 1(e), (g), and (h), obtained by removing an hexagon, a pentagon, and a pentagon plus an extra C atom, respectively, and introducing three O atoms saturating the holes. We shall mention that other small-hole structures or other closure mechanisms (with catalysts, for instance) with even lower energies can possibly exist, our construction giving just a plausible estimate of a low energy barrier. Again, we considered reactions in which the small holes close and CO_2 molecules evaporate, and we evaluated the energy difference between the initial and final states. The results are summarized in Fig. 3, which shows (solid line) these hole energies as a function of the number of carbon atoms missing in the hole. We can see in the figure that for closing the tube just 0.2 eV are needed, but a barrier of at least 4.2 eV has to be overcome first. Remarkably, the hole formation energies for the three small holes considered here are degenerate within 0.1 eV. As for the equivalent wall holes, displayed in Fig. 1(d) and (f), Fig. 3 shows (dashed line) that the tube closing is clearly exothermic (by 9.2 eV) and that no energy barrier is found.

We can understand the origin of the distinct cap and wall behaviors by defining a cap energy E_{cap} , as the energy of the capped tube minus that of the same number of atoms in the bulk of the tube. Since chemical bonds are similarly saturated at the cap and at the wall, the origin of E_{cap} must be the larger elastic energy of the cap. It amounts to 9.0 eV for the (6,6) tube, which is comparable to the 9.2 eV energy obtained for the opening of the large hole at the tube wall.

Since the release of the strain energy, which plays a crucial role in the opening process, is related to the tube diameter, narrower tubes should be more easily open due to their larger cap curvature. Our calculations on the (4,4) and (8,8) armchair tubes confirm this trend: with CO_2 molecules used as an oxygen atom reservoir, as in equation (1), the closing energy amounts to 1.2 eV for the (4,4) tube, 0.2 eV for the (6,6) tube (as we have already shown), and -0.3 eV for the (8,8) tube, allowing us to estimate a value of ~ -0.6 eV for the (10,10) tube. Therefore, within the range of experimental feasible radii [28] the CO_2 sublimation changes from endothermic to exothermic, always within tenths of eV.

The presence of an oxygen rim may have a strong influence on the ability to fill the tubes. In some cases, it may be desirable to replace it by a possibly more inert hydrogen rim. Therefore, we have studied the energetics of reducing the oxidized open tube with H_2 . Simply replacing O with H, followed by O_2 evaporation, is slightly endothermic (by 0.3 eV for the (6,6) tube). However, the reaction becomes strongly exothermic, by 9.1 and 9.5 eV, when we consider CO_2 and H_2O as byproducts, respectively. Thus, we expect that the reduction of the oxygen rim should be quite possible. We shall mention that the saturation of the tube ends with other molecular terminations rather than O or H could result in even lower

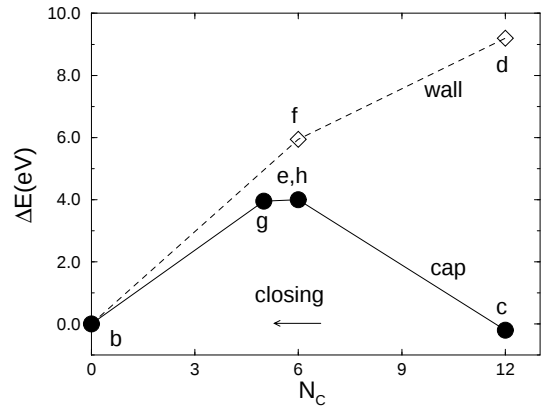


FIG. 3. Energy differences between initial and final states of the closing reaction: *tube with hole* $\rightarrow$ *closed tube* + CO_2 . The energies are shown as a function of the number of carbon atoms missing in the hole. Solid and dashed lines are used for holes at the cap and wall, respectively. The labels refer to the structures of Fig. 1.

formation energies.

In conclusion, we have studied the energetics of opening SWNT's by oxidation. We show that an oxygen rim can stabilize the edge of the open tube. The sublimation of CO₂ molecules from the rim with the subsequent closing of the tube changes from endothermic to exothermic as the tube radius increases, within the range of experimental feasible radii. Our results also show that the opening reaction occurs preferably at the tube cap, due to the release of its strain energy.

ACKNOWLEDGMENTS

We acknowledge support from the Brazilian agencies CNPq, FAPEMIG, CAPES, and PRONEX-MCT, and from Spanish DGES grant PB95-0202. P.O. is the recipient of a Motorola PCRL Sponsored Research Project. We also thank R. W. Nunes for a critical reading of the manuscript.

-
- [1] M. Dresselhaus, G. Dresselhaus, and P. C. Eklund. *Science of Fullerenes and Carbon Nanotubes* (Academic Press, San Diego, 1996).
 - [2] S. Iijima. *Nature*. **354**, 56 (1991).
 - [3] T. W. Ebbesen, P. M. Ajayan. *Nature*. **358**, 220 (1992).
 - [4] P. M. Ajayan, S. Iijima. *Nature*. **361**, 333 (1993).
 - [5] P. M. Ajayan, T. W. Ebbesen, T. Ichihashi, S. Iijima, K. Tanigaki, H. Hiura. *Nature*. **362**, 522 (1993).
 - [6] S. C. Tsang, P. J. F. Harris, M. L. H. Green. *Nature*. **362**, 520 (1993).
 - [7] D. Ugarte, A. Châtelain, W. A. de Heer. *Science*. **274**, 1897 (1996).
 - [8] A. C. Dillon, K. M. Jones, T. A. Bekkedahl, C. H. Kiang, D. S. Bethune, M. J. Heben. *Nature*. **386**, 377 (1997)
 - [9] J. Liu, A.G. Rinzler, H. Dai, J.H. Hafner, R.K. Bradley, P.J. Boul, A. Lu, T. Iverson, K. Shelimov, C.B. Huffman, F. Rodriguez-Macias, Y. Shon, T.R. Lee, D.T. Colbert, R. E. Smalley. *Science*. **280**, 1253 (1998).
 - [10] M. R. Pederson and J. Q. Broughton. *Phys. Rev. Lett.* **69**, 2689 (1992).
 - [11] Y. Miyamoto, A. Rubio, X. Blase, M. L. Cohen, S. G. Louie. *Phys. Rev. Lett.* **74**, 2993 (1995).
 - [12] J. Charlier, A. De Vita, X. Blase, R. Car. *Science* **275**, 646 (1997).
 - [13] Y. H. Lee, S. G. Kim, D. Tománek. *Phys. Rev. Lett.* **78**, 2393 (1997).
 - [14] The SIESTA program is described in Ref. [16]. It builds the DFT selfconsistent Hamiltonian in order- N operations. The Hamiltonian problem can be solved either with diagonalization (order- N^3) or with order- N algorithms according to convenience. In this study both options were used.
 - [15] P. Ordejón, E. Artacho, J. M. Soler. *Phys. Rev. B*. **53**, R10441 (1996).
 - [16] D. Sánchez-Portal, P. Ordejón, E. Artacho, J. M. Soler. *Int. J. of Quantum Chem.* **65**, 453 (1997).
 - [17] W. Kohn, L. J. Sham. *Phys. Rev.* **140**, A1133 (1965)
 - [18] J. P. Perdew, K. Burke, M. Ernzerhof. *Phys. Rev. Lett.* **77**, 3865 (1996).
 - [19] N. Troullier, J. L. Martins. *Phys. Rev. B*. **43**, 1993 (1991).
 - [20] L. Kleinman, D. M. Bylander. *Phys. Rev. Lett.* **48**, 1425 (1982).
 - [21] O. F. Sankey, D. J. Niklewski. *Phys. Rev. B*. **40**, 3979 (1989).
 - [22] The range of the orbitals is defined in a balanced way by a common orbital-confinement energy of 0.14 eV [24]. The resulting radii are 4.52 and 5.52 for the s and p orbitals of C, respectively, 5.20 for the s orbital of H, and 3.56 and 4.35 for s and p orbitals of O, all of them in atomic units.
 - [23] The split-off function reproduces the tail of the original orbital beyond some radius, matching to a smooth $r^l(a - br^2)$ towards the nucleus. The matching radius is chosen so that the split orbital carries 15 % of the norm of the original one [24].
 - [24] D. Sánchez-Portal, P. Ordejón, E. Artacho, J. M. Soler, *to be published*.
 - [25] H.S. Chen, A.R. Kortan, R.C. Haddon, M. L. Kaplan, C. H. Chen, M. Mjssce, H. Chou, and D. A. Fleming. *Appl. Phys. Lett.* **59**, 2956 (1991).
 - [26] Note that the numbers in Fig. 2(a) depend on the proposed oxidation process, and that other possibilities, like involving C and O interstitials are plausible, and would affect the results. The origin of the ambiguity is the presence of three references (bulk C, CO₂, and O₂) for defining the chemical potential of just two species, C and O. The process proposed involves no extra C atoms. However, the energy differences shown in Fig. 2(b) are independent of these assumptions. There is no ambiguity in the case of the closing process, since, in the absence of O₂, both chemical potentials are well defined.
 - [27] At growth temperatures ($\sim 3000\text{K}$), molecular dynamics simulations have shown that narrow SWNT's close spontaneously [12].
 - [28] S. Bandow, S. Asaka, Y. Saito, A. M. Rao, L. Gregorian, E. Richter, P. C. Eklund, *Phys. Rev. Lett.* **80**, 3779 (1998).